

**INNOVATIVE MECHANICAL DEVICE FOR THE POST-TENSIONING OF GFRP BARS
FOR MASONRY TYPE RETROFIT APPLICATIONS**

Piyong Yu

Graduate Research Assistant

University of Missouri-Rolla

Tel: (573) 341-6629 Fax: (573) 341-6215

Email: py4x9@umr.edu

Pedro Franco Silva, Ph.D., P.E.

Assistant Professor of Civil Engineering

University of Missouri-Rolla

Tel: (573) 341-6280 Fax: (573) 341-6215

Email: silvap@umr.edu

Antonio Nanni, Ph.D., P.E.

Vernon and Maralee Jones Professor of Civil Engineering

University of Missouri-Rolla

Tel: (573) 341-4497 Fax: (573) 341-6215

Email: nanni@umr.edu

ABSTRACT-A mechanical device especially designed for the application of low-level post-tensioning forces to glass fiber reinforced polymer (GFRP) bars was developed at the University of Missouri-Rolla. Some of the advantageous features of this device are that it is simple to assemble and the low-level post-tensioning forces can be applied manually and safely without the need for hydraulic jacks or heavy equipment. This device was conceived with the main objective of retrofitting masonry buildings, some of which remain in service despite large, open cracks leading to considerable out-of-plane instability and serviceability concerns. According to the method derived in this paper GFRP bars are installed in artificially imposed grooves and then post-tensioned with low-level stresses with the main objective to partially close these cracks, such that the serviceability and in-plane capacity of un-reinforced masonry (URM) building may be regained. The mechanical components of this device, along with its advantageous features and potential application for the retrofit of URM walls, are described in this paper.

KEY WORDS-Anchorage, GFRP bar, masonry wall, post-tensioning, prestressing, thermoplastics

Introduction

In their present form, traditional methods for post-tensioning and anchorage of steel tendons cannot be used directly for fiber reinforced polymer (FRP) bars because of difficulties associated with the gripping of FRP bars in the anchorage region. These may include damage to the FRP bar due to excessive gripping force and/or slippage of the bar out of the anchorage zone caused by low friction between the gripping mechanism and the bar. A variety of anchorage systems have been recently developed to address the poor performance of the anchorage of FRP bars.^{1,2,3,4,5,6} These can be divided into three general groups, namely: wedge, resin/grout potted, and spike systems. These systems have inevitable drawbacks in practice such as: potential for local damage to the FRP bar, curing time for resin, field setup time, and special requirement for FRP bar among many others. A hand-held device was developed in this research program to address some of these issues. This device features a simple way to simultaneously anchor and apply low-level tensile forces to GFRP bars without causing damage to the bars due to creep-rupture. Furthermore this device can be reused for future applications.

In this system, the mechanism used for the anchorage of GFRP bars was developed based on the property of thermoplastic resin, inherent to the GFRP bars produced for use with this particular device.^{7,8} Thermoplastic resins were considered for this type of application because when they are reheated they become soft, and may be remolded as necessary to achieve the desired anchorage system. In addition, it can be shown that no permanent damage is caused to either the fibers or resins in this system.

Based on this property, the GFRP bars are reheated by controlling the temperature and after the resin is softened, a wedge or a steel nail is driven into the center of the bars from the ends to create the desired anchorage mechanism. Thus, by combining the resin's thermoplastic property with this specially designed device, low-level tensile forces may be applied to GFRP bars with the main goals of increasing URM walls' strength and restoring their serviceability by closure of cracks from stressing GFRP bars placed in artificially imposed grooves.

The mechanical components of this device, assemblage, and potential application for the retrofit of URM walls are discussed in this paper.

Description Device

Features

Experimental results proved that this new hand-held device features the following characteristics:

1. Because it is a hand-held device, a hydraulic jack is not needed for stressing of the GFRP bars, which is one of the most significant features of this device.
2. This device can be used within tight spaces.
3. It can be easily transported and handled.
4. It is cost effective, because it can be reused to post-tension other bars without any limitations.

According to these beneficial features a group of only two technicians are required to assemble and work with this device to effectively retrofit masonry walls with GFRP bars

Main Components

The main components of this device are shown in Fig. 1 and may be divided in two regions:

I. Anchorage Region: the anchorage region consists of the following components and corresponding functions:

i. A wedge or nail is inserted in both ends of the heat-softened GFRP bars to create the appropriate anchorage mechanism (see Fig. 2).

ii. Steel chucks, which are commercially available from the prestressing industry, are placed around the ends of the deformed bars for gripping.

iii. PVC pipes are necessary to allow for easy cutting of the GFRP bars with a grinder/hand-held saw after the resin has cured. This is a necessary component at the dead end because otherwise the bar cannot be removed from the anchorage system. At the live end this PVC pipe facilitates the removal of the bar, but it is not an essential component.

II. Loading Region: the loading region consists of the following components:

i. A threaded pipe, constructed with four grooves cut parallel to its longitudinal axis and held in place by a load spreader and steel screws to prevent the pipe and GFRP bars from twisting during stressing. This will prevent the bars from being damaged during stressing.

ii. A load spreader, which is screwed in place with four screws to the threaded pipes to prevent twisting of the pipes.

iii. Steel screws, which are specially designed with smooth unthreaded ends for easily sliding of the threaded pipes during stressing through the load spreader.

iv. A steel nut, which is placed on the threaded pipe and is used to apply the tensile force manually with a wrench.

iv. A thrust bearing, which is commercially available and mainly used to decrease friction between the steel nut and the load spreader.

v. Plastic washers, to help in further reducing the friction between the steel nut and the thrust bearing.

In the next section, the necessary steps to accomplish the assemblage and operation of this device are described.

Assemblage

The first step in the assemblage of the hand-held device consists of providing anchorages at the ends of the GFRP bar by using a wedge or steel nail. Because of the excellent thermoplastic property of these bars, the ends of the GFRP bars can be softened using a rope heater (see Fig. 3). With the help of a temperature controller, the surface temperature of the bar can be maintained close to the glass transition temperature. After the bar ends are softened, a steel nail or wedge is manually inserted to create a slight expansion, critical for anchorage to the steel chucks (see Fig. 2). The anchorage between the bar and the steel chuck is achieved through mechanical interlock to the steel wedges, which are placed inside a steel chuck. In addition, experimental investigation has shown that no permanent damage is caused to either the fibers or resins during stressing.

After the anchorage mechanism is created, the system can be assembled according to the setup shown in Fig. 1. A key issue is that the threaded pipe should be prevented from twisting to avoid causing damage to the GFRP bars. This was accomplished by placing steel screws with smooth unthreaded ends through the load spreader. The bar can then be bonded to the structure by adopting the retrofit technique designated in the literature as Near Surface Mounted (NSM) strengthening.^{9, 10} According to this technique the GFRP bars are placed

inside grooves previously made on the surface of the member being strengthened. In this type of application either horizontal or vertical grooves are cut and cleaned in the masonry walls before operation.

In the next step, resin is placed inside the grooves and the system is put in place. The system is then fixed to the structure by tightening the steel nut in the loading region with a regular wrench, as shown in Fig. 4. Using a calibrated torque wrench, strain gages installed in the bar, and/or a load cell positioned at the dead end, the applied load is controlled to the desired level or until closure of the cracks is achieved. The complete assembled system is depicted in Fig. 5 where four rods were placed in horizontal grooves.

Finally, when the resin inside the grooves is properly cured, which usually occurs within 24 hours, the GFRP bars are cut through the PVC pipes (see Fig. 1) and the device is removed for further applications. This system was experimentally investigated in the laboratory at the component and system level and results are presented in the next section.

Experimental Evaluation

Experimental investigation was performed in two phases.⁸ These two phases are described next.

PHASE I - COMPONENT CHARACTERIZATION

The system was first evaluated with Ø6 and Ø13 GFRP bars in the laboratory at UMR according to the test setup shown in Fig. 6. The main objective of this phase was to: (1) explore ease of installation, and (2) determine stress losses. As shown in Fig. 6, the post-tensioning system was evaluated by installing the system between two steel angles, which were fixed to the ground by means of tie-downs. A load cell placed at the dead end and connected to a data acquisition system was used to measure the applied load. The bars were stressed under a sustained loading for three days and stress losses due to bar relaxation and anchorage losses were recorded during this period.

The measured tensile strength of the tested GFRP bars was 1020MPa and 689MPa, for the Ø6 and Ø13 bars, respectively (Table 1.). Test results presented in Fig. 7 show that after only one-day the stress in the bars stabilized at approximately 85% of the initially applied stress for both Ø6 and Ø13 GFRP bars. The registered load levels after three days are higher than

the limit of $0.20 f_{fu}$ imposed by ACI-440¹¹, which is used to prevent creep-rupture of GFRP bars.

Creep-rupture is a critical issue in the application of FRP materials, especially in the case of GFRP bars. According to ACI-440, after consideration of a long-term environmental factor, the stress limit for a GFRP bar is $0.2 f_{fu}$, where f_{fu} is the design strength and derived from the guaranteed tensile strength modified by a knock-down coefficient to account for environmental effects. Therefore, in the retrofit of masonry walls using pre-stressed GFRP bars consideration must be given to the creep-rupture limit, because in these applications the GFRP bars are subjected to sustained loading after pre-stressing. As such the prestress level should not exceed the creep-rupture limit. Since in these types of applications the desired prestress levels are below $0.20 f_{fu}$, creep-rupture was not an issue in this research program (although this system can post-tension GFRP bars to a higher prestress levels as shown in Fig. 7). In addition, low-level prestressing with the low-modulus of the GFRP bar is highly suitable for masonry retrofit applications. In particular, the low modulus of GFRP bars allows displacements in the masonry with low levels of prestress losses.

All of these indicate that this post-tensioning system can reliably be used to apply low-tensile forces to retrofit masonry walls without incurring significant stress losses due to bar relaxation and anchorage losses within stress levels that are limited by ACI 440 specifications.

PHASE II - RETROFIT APPLICATIONS TO MASONRY WALLS

This system has also been successfully used in laboratory conditions to stress masonry walls with the main objective of increasing their in-plane load capacity. Future tests will concentrate on studying the feasibility of this system to perform closure of existing cracks. The laboratory test setup to study the in-plane response of these walls is depicted in Fig. 8.

The bars were bonded to the masonry walls according to the NSM method and stressed in place. Next, the bars were cut through the PVC pipes (see Fig. 1). Transfer occurred at approximately 48 hours after stressing to: (1) allow for the resin to properly cure, and (2) reduce further stress losses due to the elastic shortening of the resin. After strengthening, the masonry walls were tested under monotonically increasing load up to failure. Two hydraulic jacks connected in parallel to a manual pump and positioned at one end of the wall were used to apply the desired load, as shown in Fig. 8. During testing the hydraulic jacks transmitted

the load to the walls by a series of steel shoes in order to reduce concentrated damage at the corners.

A total of 5 walls were tested to evaluate this device application to the strengthening of masonry walls (see Table 2). Wall A was constructed with no retrofit scheme and was used as the control unit to establish a baseline for performance. The remaining tested walls were strengthened with Ø6 GFRP bars stressed to percentage of levels to ultimate capacity as indicated in Table 1. For ease of test results comparison, these stress levels were normalized according to

$$nf \frac{f_{fv}}{f'_m} \frac{A_f}{A_w} \quad (1)$$

where n is the number of GFRP bars, f is the percentage of stress level to the ultimate capacity, f_{fv} and A_f are the tensile strength and cross-sectional area of the bars respectively, and f'_m and A_w are the compressive strength of masonry prisms and the vertical face area of the masonry walls where the bars were stressed against.

The number of bars used in the strengthening of each of these walls is also shown in Table 1. Each of the retrofitted walls was selected with the primary goal of comparing the increase in capacity as the number of bars increased and prestress level changed. Failure loads are also shown in Table 1. In Fig. 9 the failure loads are plotted as a function of the normalized stress computed according to Eq.(1). It is clear that the load at failure was increased as the normalized stress increased. In all tested walls failure can be characterized by a brittle mode through the development of large diagonal cracks that occurred mainly along the diagonal compression strut. Future research will concentrate in the application of this device to the retrofit of existing buildings with the main goal of exploring in further detail the features of this device previously described.

Conclusions

A mechanical device especially designed for the application of low-level post-tensioning forces to GFRP bars was discussed in this paper. Conclusions drawn from this research program are as follows:

1. The device is capable of anchoring and applying low-level tensile force to GFRP bars. Test results at the component level show that after only one-day the stress in the bars stabilized at approximately 85% of the initially applied stress.

2. No permanent damage was caused to either the fibers or resins resulting from the reheating of the bars to develop the appropriate anchorage mechanism.

3. This hand-held device is simple to implement in the retrofit of masonry walls, and can be easily reused after many applications.

4. The system is practical for the retrofit of masonry walls though the application of low-level tensile forces.

5. Increase in the in-plane capacity of masonry walls can be achieved by providing GFRP bars through the technique NSM and also by applying low-level prestressing forces to these bars.

Acknowledgements

This work was conducted with partial support from the National Science Foundation Industry/ University Research Center on Repair of Buildings and Bridges with Composites (RB2C) based at the University of Missouri-Rolla. Special thanks are due to Mr. David Vanderpool and Mr. Chris Edwards of Dow Chemicals for providing the thermoplastics-based GFRP bars and their technical assistance during the development of this research program. Also the authors would like to acknowledge some of the previous work done by Casareto, M., Oliveri, A., and Romelli, A. of University of Genoa, Genoa, Italy.

References

1. Dolan, C.W., Bakis, C.E., Nanni, A., and Munley, E., "Prestressed Concrete with FRP Composites," *Proceeding of the 3rd International Conference on Advanced Composite Materials in Bridges and Structures*, J. Humar and A.G. Razaqpur, Editors, Ottawa, Canada, ,379-386 (2000).

2. Erki, M.A., and Rizkalla, S.H., "Anchorages for FRP Reinforcement," *Concrete International*, V.15, No. 6, 54-59 (1993).

3. Al-Mayah, A., Soudki, K.A., and Plumtree, A., "Experimental and Analytical Investigation of a Stainless Steel Anchorage for CFRP Prestressing Tendons," *PCI Journal*, V.46, No. 2, 88-100 (2001).

4. Wolff, R., and Miesslerer, H.J., "Glass Fiber Prestressing System," *Fiber-Reinforce-Plastic (FRP) for Concrete Structures: Properties and Applications* (Edited by A.Nanni), Elsevier Science Publisher, New York, 305-332 (1993).

5. Burgeoyne, C.J., "Parafil Ropes for Prestressing Applications," *Fiber-Reinforced-Plastic (FRP) for Concrete Structures: Properties and Applications* (Edited by A.Nanni), Elsevier Science Publisher, New York, 333-351 (1993).
6. Nanni, A., Bakis, C.E., O'Neil, E.F., and Dixon, T.O., "Performance of FRP Tendon-Anchorage Systems for Prestressed Concrete Structures," *PCI Journal*, V.41, No. 1, 34-44 (1996).
7. Vanderpool, D.R., Micelli, F., and Nanni, A., "Thermoplastic Rebar: Performance and Applications," *Proc., CCC 2001, Composites in Construction, Porto, Portugal*, J Figuerias, L.Juvandes and R.Furia, Eds., 153-157 (2001).
8. Casareto, M., Oliveri, A., and Romelli, A., "Strengthening of Masonry: Opportunities and Challenges in the Use of Composites - Rinforzo della Muratura: Campi di Applicazione e Prospettive nell'Utilizzo dei Materiali Compositi," *Department of Structural and Geotechnical Engineering, Thesis, University of Genoa, Genoa, Italy*, 205-233 (2002).
9. Lorenzis, L.D., Nanni, A., and Tegola, A.L., "Bond of Near Surface Mounted FRP rods in Concrete Masonry Units," *Proceedings of the Seventh Annual International Conference on Composites Engineering (ICCE/7), Denver, Colorado*, 3-4 (2000).
10. Tumialan, J.G., Huang, P-C, Nanni, A., and Silva, P., "Strengthening of Masonry Walls by FRP Structural Repointing," *5th International Conference on FRP Reinforced Concrete Structures (FRPRCS-5), Cambridge, England*, 1033-1042 (2001).
11. ACI Committee 440., "Guide for The Design and Construction of Concrete Reinforced with FRP Bars (ACI 440.1R-01)," *American Concrete Institute*, 22-23 (2001).

Table 1- Material Properties

Table 2- Test Results of Masonry Walls

Fig. 1 - Hand-held device components

Fig. 2 - Inserting steel wedge in GFRP bar

Fig. 3 - Heating of GFRP bar

Fig. 4 - Manually stressing a GFRP bar with a wrench

Fig. 5 - Assembled system in a masonry wall

Fig. 6 - Test setup for component evaluation

Fig. 7 - Load relaxation of GFRP bars

Fig. 8 – Testing of retrofitted masonry walls with prestressed NSM GFRP bars

Fig. 9 - Masonry walls test results

LIST OF TABLES

TABLE 1- MATERIAL PROPERTIES

	TENSILE STRENGTH(MPa)	COMPRESSIVE STRENGTH(MPa)	ELASTIC MODULUS(GPa)
Ø6 GFRP BAR	1024		157
Ø13 GFRP BAR	689		150
MASONRY PRISM		16.75	15.08

TABLE 2-TEST RESULTS OF MASONRY WALLS

WALLS	A	B	C	D	F
QUANTITY OF Ø6 GFRP BARS	NONE	2	3	4	7
STRESSING LEVEL OF BARS (%)	0	40	25	40	25
NORMALIZED STRESS (SEE EQ.1)	0	0.55	0.58	1.17	1.28
LOAD AT FAILURE (kN)	108	205	200	211	235

LIST OF FIGURES

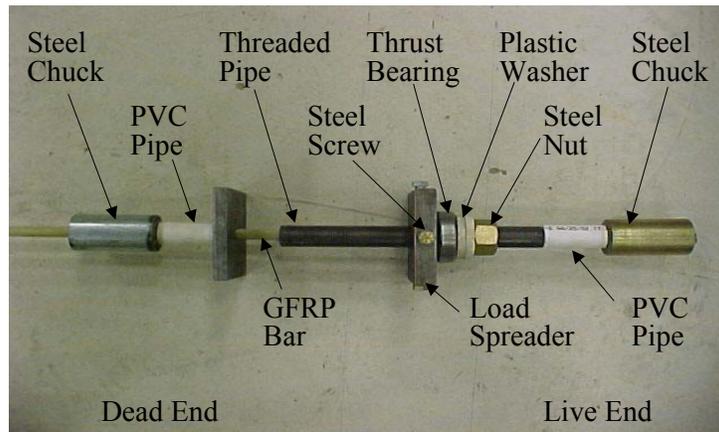


Fig. 1 - Hand-held device components



Fig. 2 - Inserting steel wedge in GFRP bar

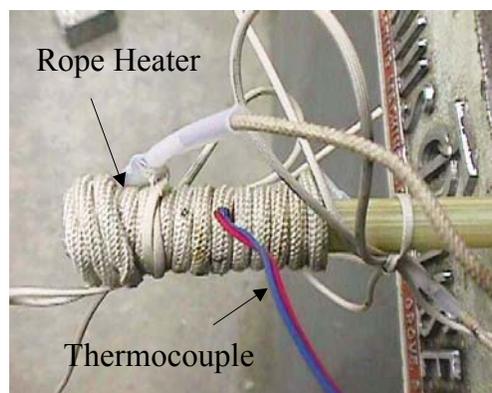


Fig. 3 - Heating of GFRP bar

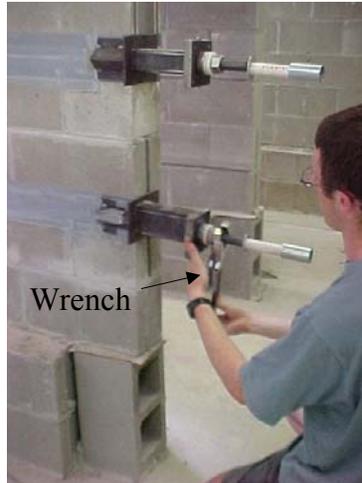


Fig. 4 - Manually stressing a GFRP bar with a wrench



Fig. 5 - Assembled system in a masonry wall

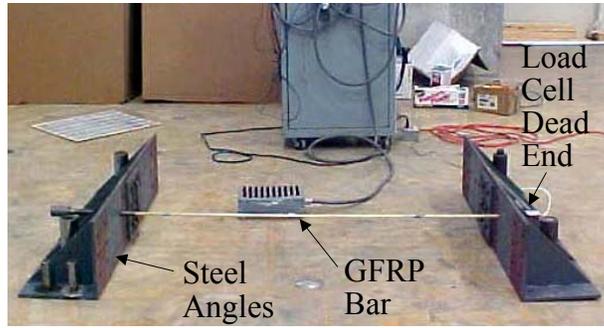


Fig. 6 - Test setup for component evaluation

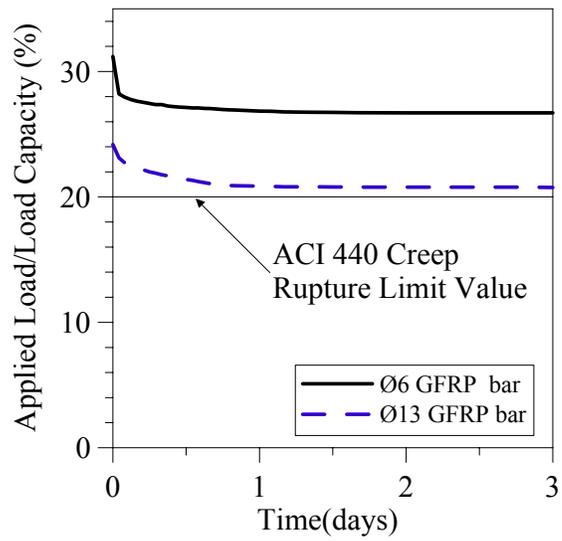


Fig. 7 - Load relaxation of GFRP bars



Fig. 8 - Testing of retrofitted masonry walls with prestressed NSM GFRP bars

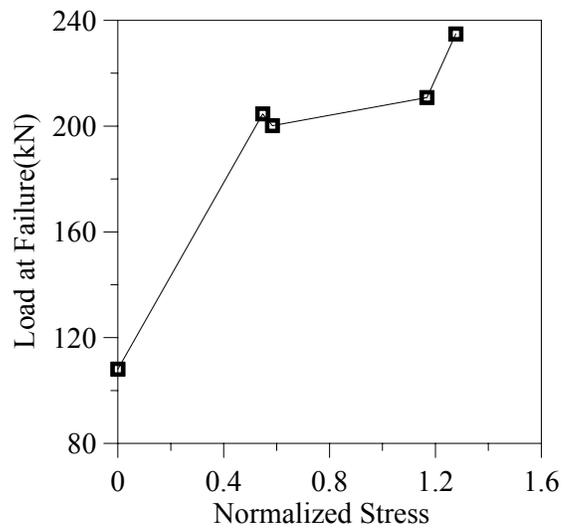


Fig. 9 - Masonry walls test results